

A Study of Selected Kenyan Anthill Clays for Production of Refractory Materials

Janet J. Kipsanai¹, Saul S. Namango², Alex M. Muumbo³

¹*Department of Mechanical & Production Engineering, Moi University*

²*Department of Chemical & Processing Engineering, Moi University*

³*Faculty of Engineering Science & Technology, Technical University of Kenya*

Abstract: Refractories are essential for all industrial processes using elevated temperatures. They play a triple role of providing mechanical strength, protection against corrosion and thermal insulation. The essential goal in the development of refractories is to obtain a useful lining life that will provide maximum furnace availability for the operators to meet production requirements at the lowest possible cost. High quality refractory at a cheaper cost is the main requirement. The aim of this study was to find out the possibility of using Kenyan anthill, as a major raw material in the production of refractory linings. Anthill clay has not been utilized in Kenya. Anthill clay was collected from Cheptebo, in the rift valley, crushed, sieved and the chemical composition determined. The samples were moulded into rectangular shaped bricks of 40mm height, 40mm width and 80mm length, allowed to dry and later fired up to a temperature of 1000^oc. Refractory properties like Compressive strength, Hardness, Linear shrinkage on firing, Apparent porosity and Density were determined. The result of chemical analysis indicated that the clay was composed of Silica (SiO₂), 52.18%; Alumina (Al₂O₃), 15.79%; Iron Oxide (Fe₂O₃), 9.41%; Calcium Oxide (CaO), 4.30%; Potassium Oxide (K₂O), 2.30%; Sodium Oxide (Na₂O), 2.81%; and other traces. The chemical analysis suggests that the clay deposit is mainly made of kaolinite and free quartz. The physical and mechanical tests show that the bricks had Cold Crushing Strength of 6,019kPa, Hardness of 17.81GPa, Linear shrinkage of 8%, Apparent Porosity of 35.21% and Bulk Density of 2.46g/cm³. Anthill clay can make better local refractory raw materials.

Keywords: Refractory, Anthill clay, cold crushing strength, hardness, density, porosity

1.0 INTRODUCTION

A refractory material retains its mechanical characteristics and inertness at high temperatures. [1] defined refractories as materials which have the ability to withstand high temperature without breaking or deforming. Any material can be described as a 'refractory', if it can withstand the action of abrasive or corrosive solids, liquids or gases at high temperatures. Refractory materials are used in linings for furnaces, kilns, incinerators and reactors. Depending on the operating environment, they need to be resistant to thermal shock and have specific ranges

of thermal conductivity and coefficient of thermal expansion. The ability to withstand exposure to heat above 538 °C is the critical distinction separating refractory from other ceramics, fibres and coating applications at only lower temperature [2].

[3], reported in his work on refractory properties of termite hills under varied proportions of additives that over 80% of the total refractory materials are being consumed by the metallurgical industries for the construction and maintenance of furnaces, Kilns, Reactor Vessels and Boilers. The remaining 20% are being used in the non-metallurgical industries as cement, glass and hard ware.

The basic functions of refractory materials according to [4] are;

1. To ensure the physical safety of personnel and installations between the hot material (the processed product) and the outer shell of the processing tool and
2. Reduce heat loss.

The more important characteristics which are required of a refractory are [1]:

- a) High melting point or high refractoriness, which is closely related to thermo-chemical stability.
- b) Mechanical strength at high temperature in terms of high refractoriness under load, high thermal shock resistance, low thermal shrinkage, low porosity and permeability.
- c) Resistance to chemical attack in the particular situation in which it is used, for instance, high resistance to corrosion by slag.

Most refractory materials are made from naturally occurring high melting point oxides. They include silica (SiO_2), Alumina (Al_2O_3), Magnesia (MgO), Chromium oxide (Cr_2O_3), Zirconia (ZrO) and iron oxide (Fe_2O_3). They are either used in natural form without any formal processing or in roasted condition [5].

It is unfortunate that despite vast clay deposits in Kenya, the Country's metallurgical industries still depend on imported refractories to meet local consumption and as a result, a lot of hard earned foreign currencies are spent in the process.

Clay is a naturally occurring material composed primarily of fine grained particles of hydrous

aluminium silicates and other minerals which show plasticity through a variable range of water content and can be hardened when dried or fired. It is also impermeable when in contact with water [6].

Basically, an anthill is a pile of clay, sand, or earth, or a combination of these materials that are excavated by the ants in the process of digging. The colony is built and maintained by an army of worker ants. These worker ants carry minute bits of earth and deposit them outside of the exit hole so that the particles do not slide back into the nest. Some variety of ants actually design and construct the anthill to specific shapes to create chambers for their various functions and purpose within the anthill. These robust structures have survived heavy rains, cyclones, sun and other adversities of nature for decades and stand tall and brave for our admiration [7].

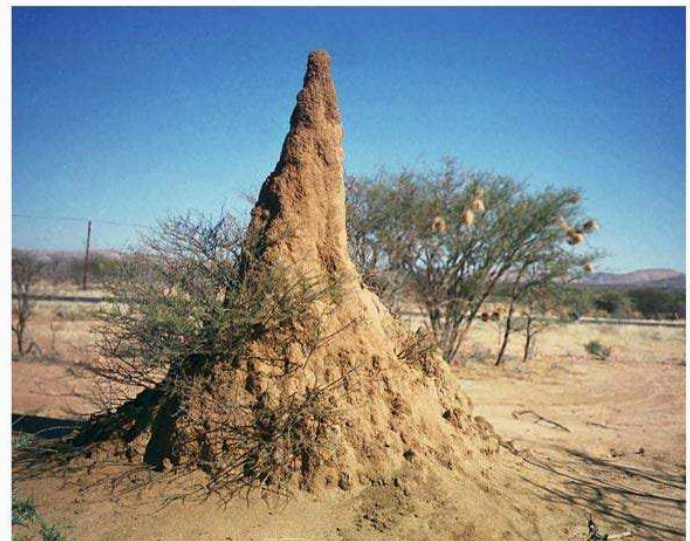


Figure 1: Anthill

According to [8], an anthill (Figure 2) is a pile of earth, sand, pine needles or clay or a composite of these and other materials that build up at the entrances

of the subterranean dwellings of ant colonies. An ant colony is an underground lair where ants live.

[7] investigated the suitability of ant hill clay as a source of ceramic raw material in Ghana. The results showed that the ant hill clay is suitable as a ceramic raw material.

2.0 RESEARCH OBJECTIVES

General Objective

To investigate the potential of anthill clay for use in the production of refractories.

Specific Objectives

1. To carry out chemical analysis of the clay under study.
2. To prepare brick samples out of the anthill clay.
3. To determine the physical and mechanical properties of the prepared samples.

3.0 MATERIALS AND METHODS

3.1 Raw material and Sample Preparation

The production of refractories begins with processing raw material. Raw material processing involves drying, crushing, grinding and determination of the Chemical Composition.

The raw materials (clays) were initially air dried and then later oven dried at 105⁰C to ensure that all the moisture had been removed.

The raw materials were then crushed using a pestle and mortar until a suitable ratio for coarse particles to fine particles was achieved

The chemical composition of the clay sample in percentage weight (wt %) of SiO₂, Al₂O₃, Fe₂O₃ and

other oxides was examined using Atomic Absorption Spectrophotometer (AAS), which was carried out at Ministry of Mining Research Laboratories Center, Nairobi, Kenya.

3.2 Development of the refractory from the raw materials

This involved the actual production of refractory from the collected raw materials to the final shaped (formed) product.

1. Mixing

The ground particles were thoroughly mixed. This was done for two purposes;

- i) For even distribution of the coarse and fine particles
- ii) For making moulding easy

2. Moulding

The brick samples were formed into the required shape and size with the aid of a wooden box type of mold which could produce three samples at one go. The test pieces of the refractory materials were made into rectangular shapes of dimension 8.0x4.0 x 4.0 cm in a mold and compacted under a hydraulic pressure of 350kN/m². 350kN/m² was determined as the optimum hydraulic pressure necessary from the work of [9].

3. Drying

The molded refractory was dried to remove its moisture. Drying was regulated so that neither voids are left in the refractory nor the refractory is shrunk to produce internal stresses. Drying was carried out very slowly and under particular set of conditions of humidity and temperature.

The sample bricks were air dried until when they were physically seen to be dry. This process undertook two months. From the drying floor the samples were then put in an oven operating at 105°C for twelve hours to remove all the remaining moisture.

4. Firing

The dried refractory was burnt for vitrification and development of stable mineral forms. In this step the already dried bricks were passed through a furnace at a controlled temperature over a certain fixed duration. The samples were fired at a temperature of 1000°C. At this temperature, the soaking time was six hours (6hrs). This is according to [10] work.

3.3 Testing of the brick samples to establish their stability characteristic properties.

3.3.1 Apparent porosity Test

Porosity of a material is defined as the ratio of its pores volume to the bulk volume. Thus porosity is an important property of refractories because it affects several other characteristics like strength, abrasion resistance, thermal conductivity and chemical stability. Porosity decreases the strength, thermal conductivity, resistance to abrasion and resistance to corrosion. On the other hand, it increases the penetration of slags, molten charge and/or gases into the refractory material and resistance to thermal spalling (thermal shock resistance). Therefore, in general, a good refractory should have lower porosity. The apparent porosity, sometimes referred to as open porosity, is a measure of the open or interconnected pores in a refractory. The apparent porosity is

determined by the volume of liquid which was absorbed by the pores when the specimen is boiled in vacuum conditions, and when the material is saturated in water.

According to [11], the porosity of a refractory has an effect upon its ability to resist penetration by metals, slags and fluxes and, in general, the higher the porosity, the greater the insulating effect of the refractory.

[12], also states that porosity and pore size distribution of a refractory will influence its thermal conductivity, in that, more porous refractory translates to a more insulating refractory.

This experiment was performed according to [13], whereby dry specimens were put in an oven maintained at a temperature of 110°C till it attained a substantially constant mass (with an accuracy of 0.01grams). The weight of the specimen (W_1) was recorded after cooling it to room temperature. The dry specimens were then immersed completely in water at atmospheric temperature for 24 hours. The specimens were taken out of water and wiped out with a cloth before being weight. The weight after removal from water was let to be, W_2 .

The respective dimensions of the samples were measured using a vernier caliper. The dimensions were then used to calculate the sample volume (V).

The apparent porosity per cent, after 24 hours immersion in cold water is given by the relation;

$$\text{Apparent porosity, } P_A = \frac{W_2 - W_1}{V} \times 100$$

Where: W_1 and W_2 is the weight of the absolutely dry specimen and the weight of the same specimen saturated in water [g], and V is the volume of the specimen [cm^3] [14].

$$\text{Volume} = \text{length} \times \text{width} \times \text{height}$$

3.3.2 Bulk density

The bulk density (BD) is the amount of refractory material within a volume (kg/m^3). An increase in bulk density of a given refractory increases its volume stability, heat capacity and resistance to slag penetration. Bulk density is the ratio weight or mass to volume and it is expressed in pounds per cubic foot or kilograms per cubic meter [15].

[11], also defines bulk density as a measure of the ratio of the weight of a refractory to the volume it occupies.

According to [12] report, the simplest way of measuring Bulk Density for uniform rectangular refractory shapes is by dividing Dry Weight by Bulk Volume which is calculated from measured dimensions. Density, porosity and permeability measurements show whether a body is fully dense, and whether therefore it can be expected to stand up to aggressive slag attack and/or penetration by process gases.

The air dried specimens were further oven dried at 110°C , cooled and weighed to the accuracy of 0.01 in order to determine their dried weight (DW). The respective dimensions of the samples were measured using a vernier caliper. The dimensions were then used to calculate the sample volume (V).

The bulk density was calculated from the equation proposed by [16].

$$\text{Bulk density, BD} = \frac{DW}{V} \text{ g}/\text{cm}^3$$

Where, DW = Dried Weight V = Volume

$$\text{Volume} = \text{length} \times \text{width} \times \text{height}$$

3.3.2 Cold crushing strength

Cold crushing strength is the resistance of the refractory to compressive loads. As per [17], a cold crushing strength test is used to measure the cold strength of a brick. It is used to show whether or not the brick has been properly fired. This test, generally a quality control check, also indicates whether the brick will damage to corners and edges in transport. Cold crushing strength is the maximum load at failure per unit of cross-sectional area when compressed at ambient temperature.

The dried test bricks produced from the anthill clay, were oven dried at a temperature of 110°C for 12 hours. It was then cooled to room temperature. The specimen was then taken to the compressing test machine where load was applied until cracks were noticed. The load at which the specimen cracked was noted, which represents the load required for determining cold crushing strength of the test specimen.

The test was carried out in accordance with [18]. Cold Crushing Strength was then calculated using Equation;

$$\text{CCS} = \frac{\text{Maximum load (kN)}}{\text{Cross-sectional area (m}^2\text{)}} = \frac{P}{A}$$

Where, CCS = Cold Crushing Strength P = Applied Load A = Area of Load Applied

A good refractory material must possess high mechanical strength to bear the maximum possible load without breaking.

3.3.2 Linear shrinkage

Linear shrinkage represents the permanent change that the refractory shapes undergo on heating or after reheating under a given set of conditions. The drying of clay is always accompanied by shrinkage. As the film of water between the clay particles is drawn off by evaporation the particles draw closer together to close up the interstices. The effect of this action is the shrinkage of the entire mass of clay.

To determine the fitness of a particular brick for service, it is often tested for shrinkage under temperature conditions equivalent to those which it would receive in use. This is done by first determining the length or volume of the brick by measurement and then subjecting it to a prolonged heating at the desired temperature. After the brick has cooled, it is again measured and the length, volume and shrinkage determined.

A slanted line of length 6cm was inserted horizontally on each piece and recorded as (L_1). The test pieces were then placed inside the furnace and fired up to 1000°C and the line drawn across the horizontal axis of the pieces was measured to determine its final length (L_2) after firing. The linear shrinkage of the materials was determined with equation;

$$\text{Linear shrinkage (\%)} = \frac{L_1 - L_2}{L_1} \times 100$$

The test was carried out in accordance with [19].

3.3.3 Hardness test

Hardness is a characteristic of a material, which can be defined as the resistance to indentation, and it is determined by measuring the permanent depth of the indentation. Measuring the hardness of a ceramic is important and this is usually done using an indentation test. The basic idea is that a permanent surface impression is formed in the material by an indenter. The actual or projected area of the impression is then measured. The hardness is then determined by dividing the applied force, F , by this area [20].

In this study, hardness was determined using the Brinell method. The Brinell method applies a predetermined test load (F) to a carbide ball of fixed diameter (D) which is held for a predetermined time period and then removed. The resulting impression is measured across at least two diameters – usually at right angles to each other and these result averaged (d).

In this experiment, the indenter diameter (D) used was 5mm and the test force (F) was 1kN.

Typically, an indentation is made with a Brinell hardness testing machine and then measured for indentation diameter in a second step with a specially designed Brinell microscope or optical system. The resulting measurement is converted to a Brinell value using the Brinell formula or a conversion chart based on the formula.

Equation below illustrates the formula used to obtain the Brinell value.

$$HB = \frac{0.102F}{0.5\pi D(D - \sqrt{D^2 - d^2})} \text{ N/m}^2$$

Where F = Force, D=Ball Diameter, d = diameter of indentation.

at a constant force of 1kN, and a ball diameter of 5mm

4.0 RESULTS AND DISCUSSION

The results from the experimental work are given in tables 1 and 2. From table 1, it is evident that anthill clay has silica and alumina as the predominant substances and it could be concluded that it is siliceous in nature and is of the Alumino-silicate family.

The sample has high silica content well above the ideal 46.51% for clay which makes it be able to withstand fairly high temperatures [6]. From [21] report, the silica content of anthill satisfies the standards for the manufacture of refractory bricks and high melting clay with values 51.70 and 53-73% respectively; but below the range for the manufacture of ceramics and glass formulation.

The alumina (Al_2O_3) content of the sample is not high and is about 16%. This means that, the value falls below the standards required for the manufacture of ceramics, refractory bricks, paper and paints. However, the anthill clay can still be used to manufacture high melting clay and alumino-silicate fiber glasses since they require 16-29% and 12-17% of Aluminium Oxide respectively as reported by [21].

The sample clay has a fairly high iron content (Fe_2O_3) which makes it fire terracotta red (brick red) color on firing [9].

The Loss on Ignition of the anthill clay (LOI) was determined as the percentage of moisture loss to ignition on firing. This represents the amount of moisture the clay material could hold or percentage weight reduction of the soil sample which may probably be a reflection of its grain structure and fineness. Following the report by [21], the loss on ignition of the sample falls within the standard range for the production of ceramics, refractory bricks and high melting clay. [22] suggests that the loss on ignition values, are required to be low in order to reduce on the effect of porosity on the final products.

The physical test results of anthill clay showed an apparent porosity of 35.21% which according to [23], qualify to be used as refractory firebricks.

The bulk density of 2.4 g/cm^3 was obtained which according to [24] makes them qualify to be used as fireclay refractories.

The Cold crushing strength of the anthill bricks obtained was 6018.73 Kpa. This value falls within the standard range for the manufacture of thermal insulators as given by [25]. According to Kumar, the standard range is 981-6867kPa.

Table 1: Chemical composition analyses of Anthill clay compared with standard clay for industrial applications [21].

Composition	Anthill Clay	Ceramics	Refractory Brick	High melting clay	Glass	Paper	Paint
SiO₂	52.19	60.5	51.7	53-73	80-95	45-45.8	45.3-47.9
Al₂O₃	15.79	26.5	25-44	16-29.0	12-17.0	33.5-36.1	37.9-38.4
Fe₂O₃	9.41	0.5-1.2	0.5-2.4	1-9.0	2-3.0	0.3-0.6	13.4-13.7
CaO	4.30	0.8-3.0	0.1-2.0	0.5-2.6	4-5.0	0.03-0.6	0.03-0.6
K₂O	2.30	-	-	-	-	-	-
TiO₂	1.13	-	-	-	-	-	-
CuO	-	-	-	-	-	-	-
V₂O	-	-	-	-	-	-	-
LOI	9.77	8-18.0	8-18.0	5-14.0	-	-	-

According to [22], the total percentage shrinkage for standard fireclay and siliceous refractories are supposed to be ranging between 4-10%. The total percentage shrinkage value obtained from the brick samples was 8% thus falling within the acceptable range.

The hardness value obtained from the fired anthill bricks was 17.81GPa which falls between the highest and least hardness values for ceramics as given by [20]. It is reported that MgO has the least hardness value of 3.63GPa while Diamond is the hardest with a value of 78.48 GPa.

Table 2: Physical and Mechanical test results

Sample description	Tested properties				
	Apparent Porosity (%)	Bulk Density (g/cm ³)	Cold Crushing Strength (kPa)	Linear Shrinkage (%)	Hardness (GPa)
Anthill Brick	35.21	2.4	6018.73	8	17.81

5.0 CONCLUSION AND RECOMMENDATION

5.1 Conclusion

An experimental study was conducted to investigate the suitability of Anthill clay as industrial raw material for making refractories in view of their chemical, mechanical and physical properties.

The results of the chemical analysis showed that the clay contain aluminum oxide (Al₂O₃) and silica (SiO₂) as major constituents making it suitable as aluminosilicate refractory material.

The batch samples passed through the experimental tests to determine their refractory properties in terms of mechanical and physical behaviors showed that the selected raw material (clay) can substitute for the imported refractories either as thermal insulators or as service refractory linings (bricks). The cost of refractories will also reduce since they can be obtained locally.

The chemical composition results also suggested that the clay is found to be a source of local raw materials for the production of refractory bricks and high melting clays.

The results of the investigation will be very useful and serve as a database for prospective investors and managers of metallurgical industries.

It can therefore be concluded that Anthill clay can substitute for the imported refractory raw materials.

5.2 Recommendation

The clay under study, that is, anthill, has not been identified in Kenya for the production of refractories. Thus if this clay is exploited and harnessed, it will no doubt provide an internal source of raw materials.

There is also the need for geological survey to determine the extent of the deposits.

ACKNOWLEDGMENT

The authors wish to thank Moi University, Ministry of Mining and Eldoret Polytechnic for their support.

REFERENCES

- [1] Omotoyinbo, J.A and Oluwole, O.O. 2008. Working Properties of Some Selected Refractory Clay Deposits in South Western Nigeria. *Journal of Minerals & Materials Characterization & Engineering*, 7(3): 233-245.
- [2] Musa, U., Aliyu, M.A, Mohammed, I. A, Mohammed, A. D, Sadiq, M.M. and Isah, A.G. 2012. A Comparative Study of the Refractory Properties of Selected Clays in Niger State, Nigeria. *Journal of Advances in Biotechnology & Chemical processes*, 1(2): 1-5.

- [3] Mohammed B.N. (2009). Refractory properties of termite hills under varied proportions of additions. *The Journal of the Institution of Metals*. 2 (10): 625.
- [4] Boch P. and Niepce J. C. 2007. *Ceramic materials*. Processes, properties and applications. ISTE Ltd, USA.
- [5] Aigbodion V.S., Atuanya C. U. and Chikaodi C. D. 2013. Effect of Tin Tailings on Some Refractory Properties of Alumino-Silicates (Alkaleri) Clay. *Journal of Minerals and Materials Characterization and Engineering* 1: 29-32
- [6] Shackelford J.F. and Doremus R.H.2008. *Ceramic and Glass materials*. Structure, properties and processing. Springer press, New York.
- [7] George A. H. 2009. Anthill as a resource for ceramics. Doctoral thesis, University of Science and Technology Kumasi, Ghana.
- [8] Stone and Ndu. 1985. *New Biology for West African Schools*. Longmans Group Ltd, New York.
- [9] Nnuka, E.E & Agbo,U.J.E. (2000), Evaluation of the Refractory Characteristics of Otukpo clay deposits, N.S.E. *Technical Transaction* .35(1):34-36
- [10] Aliyu S., Garba B., Danshehu B.G., Argungu G. M., and Isah A. D. (2014) Physio-chemical Analysis of Gwarmi Clay Deposit, Wurno Local Government Area of Sokoto State, Nigeria. *The International Journal Of Engineering And Science (IJES)*, 3(6):62-67
- [11] Harbison-Walker, 2005. *Handbook of Refractory Practice*. Harbison-Walker Refractories Company, Moon Township, PA. Retrieved November 30, 2015 from <http://www.somitmurni.com/Handbook.pdf>
- [12] Berger M.B. 2010. The importance and testing of density, porosity, Permeability and pore size for refractories. *The Southern African Institute of Mining and Metallurgy; Refractories 2010 Conference*. 1(1): 101-116
- [13] Singh S. 1993. *Engineering Materials*. Konark publishers PVT LTD, Delhi.
- [14] Shaw K. 1972. *Refractories and their uses*. Applied Science Publishers LTD, London.
- [15] Aggarwal O.P. 2001. *Engineering Chemistry*. Khanna Publishers, New Delhi.
- [16] Ekwere, I. I. 2009 . Characterization of Some Nigeria Clays for Ceramic Application. In; *Proceedings of 1st National Conference of Faculty of Technology*, Obafemi Awolowo University, pp. 32-37.
- [17] Surendranathan A. O.2015.*An Introduction to Ceramics and Refractories*. CRC Press-Taylor & Francis Group, New York.
- [18] ASTM. 2008. Standard Test Methods for Cold Crushing Strength and Modulus of Rapture of Refractories.
- [19] ASTM. 2010. Standard Test Method for Drying and Fired Shrinkages of Ceramic White ware Clay.

[20] Carter C. B and Norton M.G. 2007. Ceramic Materials. Science and Engineering. Springer, London.

[21] Chester J.H. 1973. Refractories, production and properties. Iron and steel institute, London.

[22] Omowumi O.J. 2000. Characterization of some Nigerian clay as refractory materials for furnace lining. Nigerian found of engineering management 1(1): 1-4

[23] Schacht A. C. 2004. Refractories handbook. Marcel Dekker press, New york.

[24] Gilchrist J.D. 1977. Fuels, Furnaces and Refractories. Pergamon Press, New york.

[25] Kumar R. 2011. Development of Low Bulk Density Fireclay Insulation Brick. A Master's Thesis Retrieved November 30, 2015 from http://ethesis.nitrkl.ac.in/2579/1/rahul1_project_final.pdf

AUTHORS

Janet J Kipsanai

Graduate Assistant

Department of Mechanical & Production Engineering
Moi University

Saul S. Namango

Associate Professor

Department of Chemical & Processing Engineering
Moi University

Alex M. Muumbo

Associate Professor

Faculty of Engineering Science & Technology
Technical University of Kenya

Correspondence Author

Janet J Kipsanai,

kipsanaij@yahoo.com,

+254723769078.